

# The Effect of Milling Times and Annealing on Synthesis of Strontium Titanate Ceramics

Rahmat Doni W<sup>1</sup>, Azwar Manaf<sup>2</sup>, Viktor Vekky Ronald Repi<sup>3</sup> and Dony Hidayat Al Janan<sup>4</sup>

<sup>1,4</sup>Department of Mechanical Engineering, Semarang State University, Semarang 50221, Indonesia

<sup>2</sup>Material Science, Department of Physics, University of Indonesia, Depok 16424, Indonesia

<sup>3</sup>Department of Physical Engineering, National University, Jakarta 12520, Indonesia

rahmat\_doni@yahoo.com<sup>1</sup>

**Abstract**—Analysis of microstructure of Strontium titanate (SrTiO<sub>3</sub>) phase obtained by milling and annealing of SrCO<sub>3</sub> and TiO<sub>2</sub> precursors. However, the material properties for strontium titanate require a careful control of crystallite structure as well as microstructure design to meet a specific application. The mixture of strontium carbonate (SrCO<sub>3</sub>) and titanium oxide (TiO<sub>2</sub>) powders was used to obtain SrTiO<sub>3</sub> phase by using vibrator ball mill with ball to powder ratio 10:1 and heat treatment processes. The size of powder particles was determined by a laser particle analyzer (PSA). The X-ray diffraction methods were used for qualitative, quantitative phase analyses and for crystallite size and lattice distortion determination. The milling process of strontium carbonate and titanium oxide mixture causes decrease of the mean particle size and crystallite size of involved phases. The X-ray diffraction investigations of SrCO<sub>3</sub> and TiO<sub>2</sub> mixture milled for 60 hours and annealed at 900 °C with 3 h of holding time enabled the identification of SrTiO<sub>3</sub> phase. Annealing the sample of the particles at 900 °C has resulted in a dense compact and promoted the formation of particles containing nanocrystallites. The crystallite-growth samples of SrTiO<sub>3</sub> phase were dependent on temperature and time of their annealing.

**Keywords**—particle size, crystallite size, strontium titanate, mechanical milling, annealing.

## I. INTRODUCTION

Alkaline earth metal titanates are becoming increasingly important in the ceramic and electronic industries where, in particular, BaTiO<sub>3</sub> and SrTiO<sub>3</sub> are widely employed. Strontium titanate (SrTiO<sub>3</sub>) is a paraelectric cubic structured perovskite material at room temperature. It exhibits a large dielectric constant of ~300 of the sintered ceramics. At temperatures <105 K, its cubic structure transforms to tetragonal ferroelectric phase. Furthermore, SrTiO<sub>3</sub> (STO) has various physical properties because of its ferroelectricity, thermoelectricity with a thermal conductivity of 12 Wm<sup>-1</sup>K<sup>-1</sup>, photocatalysis and superconductivity at temperatures <20 K [1]. Piezoelectric response has been presented on STO, which exhibits a rapidly increasing piezoelectric response with decreasing temperature below 50 Kelvin; the magnitude of its response around 1 Kelvin is comparable to that of the best materials at room temperature [2]. In addition, it has good mechanical strength with the Mohs hardness of 5.5, high thermal and chemical stability, low dielectric loss, a low coefficient of thermal expansion of 9.4x10<sup>-6</sup> °C<sup>-1</sup>, a high melting temperature of 2080°C, a refractive index of 2.31–2.38 nearly identical to that of

the diamond and semiconductor with a band gap of 3.2 eV [3,4]. STO has been applied in *radio* and *microwave-frequency tunable capacitor device*, *metal-insulator-metal (MIM) capacitors* [5], and *dynamic random access memories (DRAMs)*[6].

There were many synthesis methods applied to STO including conventional mixture oxides [7], microwave synthesis [8], mechanochemical [9], coprecipitation [10], and sol-gel [11]. The microstructure and the processing for each are quite different. The convenient method for the production of fine and nanocrystalline materials is mechanical milling by a ball-milling technique which has also being adapted to the preparation of strontium titanate. The technique is considered simple and less costly able to produce powders which compose of very fine particles in the range of single-domain particles (~1 μm) [12,13]. In solid-state synthesis, a single phase SrTiO<sub>3</sub> could be obtained only after calcination of the reaction mixture at high temperature (1000–1200°C)[14].

In this work, we report some results of materials characterization especially particle and grain sizes which were promoted during mechanical milling and annealing of a SrTiO<sub>3</sub> ceramics. Discussion are including results of mean particle size characterization by a Laser Particle Size Analyzer and mean crystallite size determination by means of line broadening analysis employing a step scanning counting in the X-ray diffraction (XRD) apparatus.

## II. EXPERIMENTAL METHOD

SrTiO<sub>3</sub> (coded STO) were obtained from the mixture of strontium carbonate SrCO<sub>3</sub> and titanium (IV) oxide TiO<sub>2</sub> powders, by using high-energy ball milling and heat treatment processes. Stoichiometric quantities of the analytical-graded precursors SrCO<sub>3</sub> and TiO<sub>2</sub> with purity better than 98 % were mixed and milled in a vibratory ball mill for 60 hours. The weight ratio of balls to milled material was 1:10. After milling process the diameter sizes of examined powder particles were determined using Particle Size Analyzer (PSA) Coulter LS100. Phase analysis and crystallite size of milled powders were carried out using the X-ray Philips diffractometer equipped with Co K α radiation. The X-ray diffraction patterns were recorded by “step-scanning” method in 2θ range from 20° to 100° and 0.005° step. The powders were annealed in the electric chamber furnace (Thermolyne 46100C) at 550, 750, 900 and 1000°C in the

air under atmosphere pressure for 0, 3, 5, 12, and 24 hours respectively. The Rietveld analysis was performed applying High Score Plus program that is an update version for Rietveld refinement with PC and mainframe computers. The pseudo-Voigt function was used in the describing of diffraction line profiles at Rietveld refinement. The crystallite sizes and lattice distortions for SrCO<sub>3</sub> and TiO<sub>2</sub> also SrTiO<sub>3</sub> phases were estimated using Williamson-Hall method [15].

### III. RESULTS AND DISCUSSION

The diffraction patterns of SrCO<sub>3</sub> and TiO<sub>2</sub> precursors (Fig. 1) which these were matched diffraction patterns of SrCO<sub>3</sub> and TiO<sub>2</sub> in *data base Inorganic Crystal Structure Database (ICSD)* number 98-016-6088 dan 98-007-6177 respectively.

Fig. 2 are showing results of evaluation for mean particle size of SrCO<sub>3</sub> and TiO<sub>2</sub> mixture up to 60 hours of milling. All the sample powders go through the four stages of the mechanical alloying process, namely:

(a) initial stage; (b) intermediate stage; (c) final stage; (d) completion stage [16]. It shows that mean particle sizes of mechanically milled for SrCO<sub>3</sub> and TiO<sub>2</sub> mixture in initial or early stages of milling are characterized by the increase in the mean size due to incorporation of particles of component compounds. The largest mean particle size were achieved after 10 hours milling times. However, the mean particle size of SrCO<sub>3</sub> and TiO<sub>2</sub> mixture is ~16 μm. Extension of milling time beyond 10 hours have decreased progressively the mean size towards a settle value. Long terms of mechanical treatment during advanced stages of mechanical alloying have caused particles experiencing embitterment due to accumulation of internal stresses [17]. Continuous plastic deformations to the brittle particles should caused further reduction in particle size towards an average value of ~ 2 μm and eventually settle down to that value even if the deformation continues to grow after the duration of 60 hours milling time at completion stage.

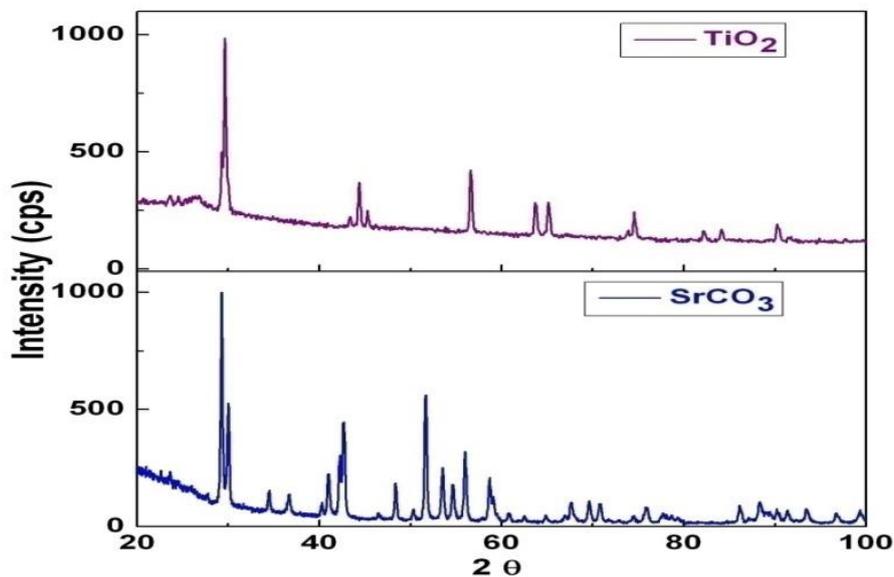


Figure 1. X-ray diffraction patterns of SrCO<sub>3</sub> and TiO<sub>2</sub> precursors

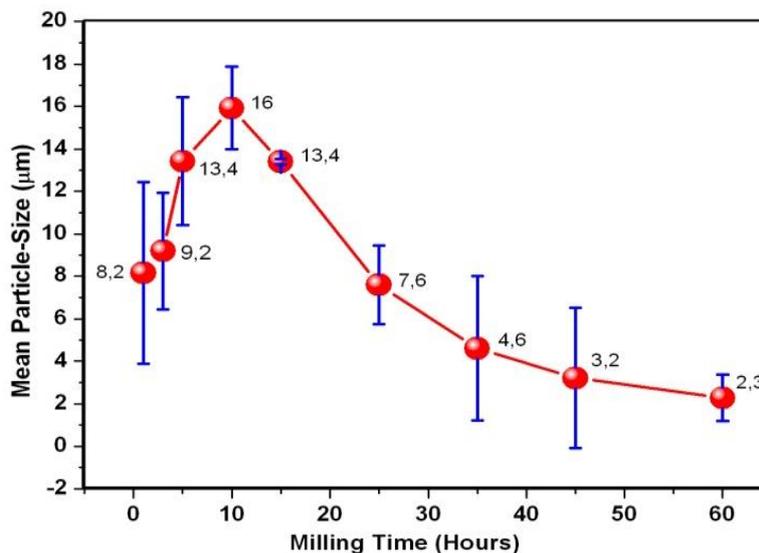


Figure 2. The mean particle size of SrCO<sub>3</sub> and TiO<sub>2</sub> mixture as function of milling time

In Fig. 3, the comparison of diffraction patterns of SrCO<sub>3</sub> and TiO<sub>2</sub> mixture after 5, 15, 35 and 60 hours of milling process is shown. Identification of the diffraction peaks ensured that the all peaks are matched with that of SrCO<sub>3</sub> and TiO<sub>2</sub> phase. In addition, in Fig. 3 shows the broadening of diffraction lines and decrease of their intensity. These effects indicate that ball milling causes decrease of the crystallite size of tested phases and leads to homogenizing the milled mixture.

In Fig. 4, as the result of milling process the mean crystallite size of SrCO<sub>3</sub> and TiO<sub>2</sub> phases diminishes to 17 nm and 19 nm, respectively of the milling time up to 60 hours.

The X-ray diffraction investigations of SrCO<sub>3</sub> + TiO<sub>2</sub> powder mixture milled for 60 hours and after different temperature and times of annealing treatment up to 900°C (Fig. 5). The sample was crystallized to cubic strontium

titanate single phase after annealing at 900 °C for twenty four hours in air. The lattice constant calculated from the XRD data is 3.906Å that agrees with the reported XRD data in Inorganic Crystal Structure Database (ICSD) number 98-002-3076 with shaped cubic perovskite crystal structure for SrTiO<sub>3</sub>. To know for sure, temperature and time of the most optimum is achieved in the transformation process into a single phase STO phase in full, then it should be tested thermal analysis.

The intensity and sharpness of the X-ray diffraction (XRD) peaks of STO phase were found to increase with annealing temperature at 900 °C up to 24 hours. The increase in intensity and sharpness of the XRD peaks with annealing temperature may be attributed to the increase in the grain or crystallite size thereby increasing packing density of the samples annealed at higher temperature.

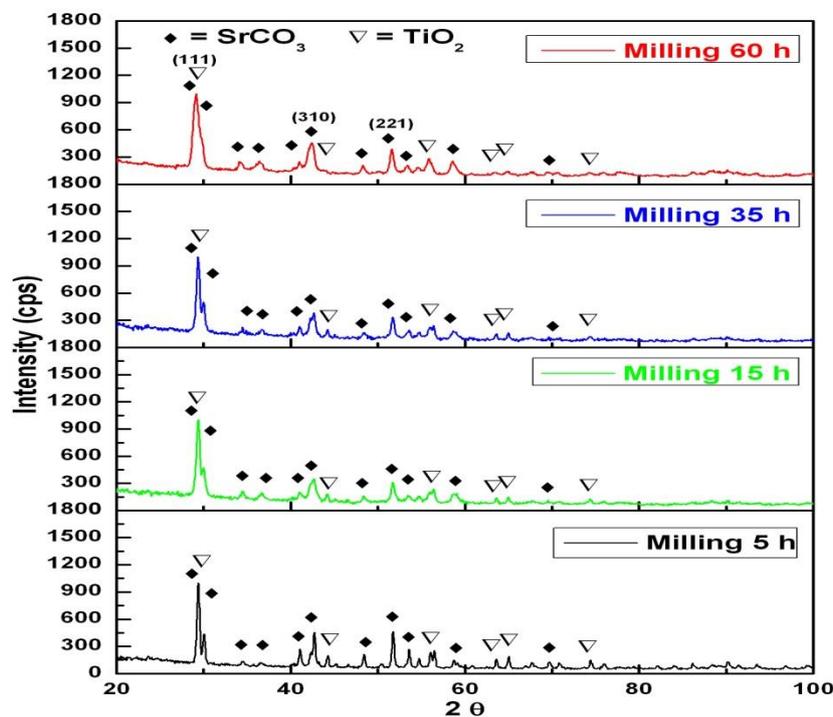


Figure 3. X-ray diffraction patterns of SrCO<sub>3</sub> and TiO<sub>2</sub> mixture up to 60 hours of milling

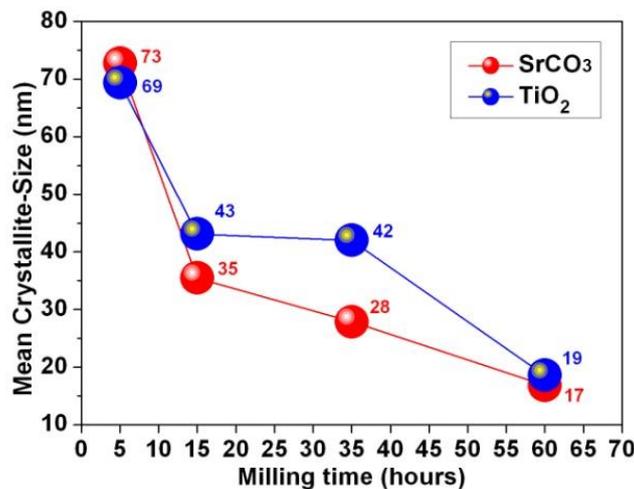


Figure 4. The mean crystallite size of SrCO<sub>3</sub> and TiO<sub>2</sub> mixture up to 60 hours of milling

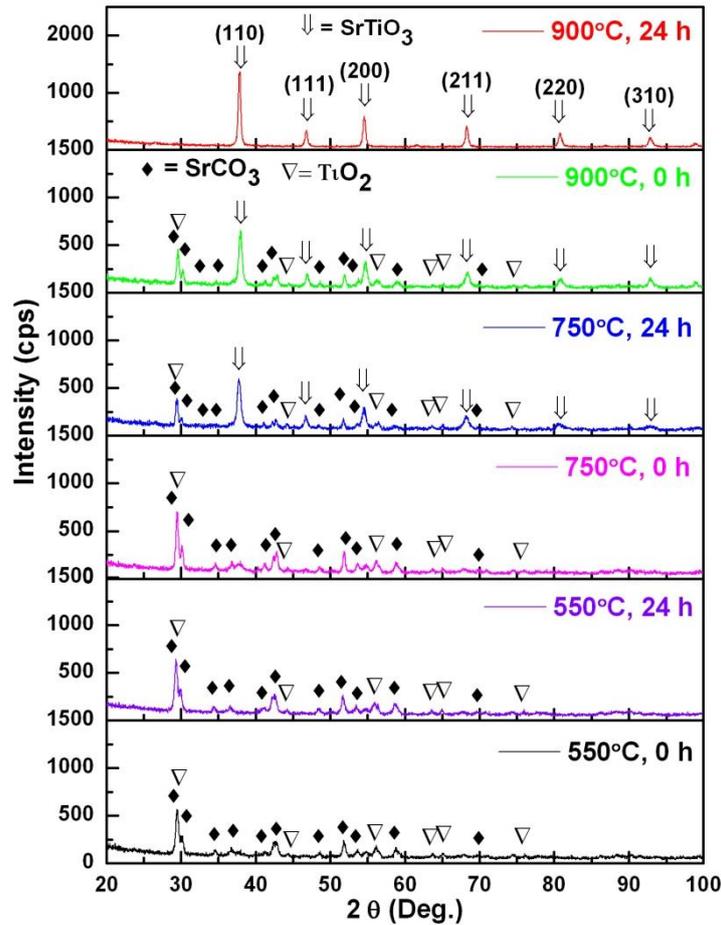


Figure 5. X-ray diffraction profile of SrCO<sub>3</sub> and TiO<sub>2</sub> mixture after annealing up to 900°C.

#### IV. CONCLUSION

The investigations performed on the SrCO<sub>3</sub> and TiO<sub>2</sub> mixture after milling and heat treatment allowed to formulate the following statements:

- High-energy milling of studied of SrCO<sub>3</sub> + TiO<sub>2</sub> powder mixture milled for 60 hours results in the decrease mean particle size to ~ 2 μm and crystallite size to 17 nm and 19 nm, respectively.
- Heating of the particles results in the mechanical integration of the sintering temperature of 900 °C promote the formation of crystallites with nanometer-scale size and material make the integration of mechanical and sintering the material with a particle containing nanocrystallite.
- SrTiO<sub>3</sub> ceramic has been prepared by mechanical alloying processing technique. The as fired powder was found to be amorphous and crystallized to cubic SrTiO<sub>3</sub> after annealing up to 900 °C for twenty hours. Dense ceramic samples were obtained by annealing at different temperatures and holding times.

#### ACKNOWLEDGMENT

The authors acknowledge the support from Materials Science UI and Mechanical Engineering UNNES for research facilities. This work was funded by Competitive Research Grant (*Hibah Bersaing*) DIPA under contract no. 023.4.1673453/2015 sponsored by the State Ministry of Research, Technology and DIKTI.

#### REFERENCES

- [1] Brankovic G, Brankovic Z, Varela JA, Longo E, Strontium titanate films prepared by spray pyrolysis, *Journal of Europe Ceramic Society* 24: 6 (2004) 989-991.
- [2] Grupp DE, Goldman AM. Giant piezoelectric effect in strontium titanate at cryogenic temperature, *Science* 276 (2011) 392-394.
- [3] George CN, Thomas JK, Jose R, Kumar HP, Suresh MK, Kumar VR, Wariar PRS, Koshy J, Synthesis and characterization of nanocrystalline strontium titanate through a modified combustion method and its sintering and dielectric properties, *Journal of Alloys and Compound* 486 (1-2) (2009) 711-715.
- [4] Ianculescu A, Braileanu A, Voicu G, Synthesis, microstructure and dielectric properties of antimony-doped strontium titanate ceramics, *Journal of Europe Ceramic Society*, 27 (2-3) (2007) 1123-1127.

- [5] Chiang KC, Huang CC, Chen GL, Chen WJ, Kao HL, Wu YH, Chin A, McAlister SP. High-performance SrTiO<sub>3</sub> MIM capacitors for analog applications. *IEEE Transactions on Electron Devices* 53 (2006) 2312–2319.
- [6] Pontes FM, Leite ER, Lee EJH, Longo E, Varela JA. Preparation, microstructural and electrical characterization of SrTiO<sub>3</sub> thin films prepared by chemical route, *Journal of the European Ceramic Society* 21 (2001) 419-426.
- [7] Berbenni V, Marini A, Bruni G. Effect of mechanical activation on the preparation of SrTiO<sub>3</sub> and Sr<sub>2</sub> TiO<sub>4</sub> ceramics from the solid state system SrCO<sub>3</sub> –TiO<sub>2</sub>, *Journal of Alloys and Compounds* 329 (2001) 230-238.
- [8] Liu HX, Li YW, Ouyang SX. Heating effect in microwave field and microstructure of BaTiO<sub>3</sub>. *Sci China (Ser A)* 40 (1997)779–84.
- [9] Wang J, Yin S, Zhang Q, Saito F, Sato T. Mechanochemical synthesis of SrTiO<sub>3</sub>- x Fx with high visible light photocatalytic activities for nitrogen monoxide destructive, *Journal of Materials Chemistry* 13 (2003) 2348-2352.
- [10] Lee J, Shin HC, Choi JC, Choi SC. The electric properties of SrTiO<sub>3</sub> varistor prepared by co-precipitation process. *Journal of Micro Packaging Society* 7 (3) (2000) 7–11.
- [11] Wang Xuewen, Zhang Zhiyong, Zhou Shuixian. Preparation of nano-crystalline SrTiO<sub>3</sub> powder in sol-gel process, *Materials Science and Engineering B* 86 (2001) 29-33.
- [12] Mendoza-Suarez G, Matutes-Aquino JA, Escalante-Garcia JI, Mancha-Molinar H, Rios-Jara D, Johal K.K. Magnetic properties and microstructure of Ba-ferrite powders prepared by ball milling, *Journal of Magnetism and Magnetic Materials* 223 (2001) 55-62.
- [13] Ding J, Street R, Nishio H. Magnetic Properties of Ba-and Sr-hexaferrite prepared by mechanical alloying, *Journal of Magnetism and Magnetic Materials* 164 (1996) 385-389.
- [14] Qi-An Zhu, Jun-Gu Xu, Shang Xiang, Li-Xia Chen, Zhi-Gang Tan, Preparation of SrTiO<sub>3</sub> nanoparticles by the combination of solid phase grinding and low temperature calcining, *Materials Letters* 65 (2011) 873–875.
- [15] Williamson GK, Hall WH, X-ray line broadening from filed aluminium and wolfram, *Acta Metallurgica* 1 (1953) 22-31.
- [16] Lü L, Lai M.O, *Mechanical Alloying*, (1998) Kluwer Academic Publishers, pp. 11–21.
- [17] Suryanarayana C, *Mechanical Alloying and Milling*, (2004) Marcel Dekker, New York.